



The Chemical Company

RHEOCRETE[®] CNI

Corrosion-inhibiting admixture for steel reinforced concrete

Description of Product

RHEOCRETE CNI is a calcium nitrite-based corrosion-inhibiting admixture for steel reinforced concrete. RHEOCRETE CNI admixture contains a minimum of 30% active ingredients by mass and meets ASTM C 494 interim requirements for Type C, Accelerating Admixtures.

Benefits

- Provides basic corrosion protection for steel reinforced concrete structures
- Provides effective corrosion protection against chlorides in concrete
- Extends the service life of reinforced concrete structures

Packaging

RHEOCRETE CNI admixture is available in 210ltr drums.

Mechanism

In the alkaline environment of concrete, a natural passive ferric oxide layer forms on the surface of embedded reinforcing steel and protects the steel from corrosion. This passive oxide layer may break down in the presence of chlorides and moisture resulting in corrosion of the steel.

RHEOCRETE CNI admixture delays corrosion by repassivating defects on the steel surface. These defects are ferrous oxide ions that are susceptible to chloride attack.

When chloride ions attack the ferrous ions, they combine to create a ferrous chloride complex (rust) and initiate pitting corrosion on the reinforcing steel. If untreated, chloride ions continue to attack newly exposed ferrous ions and form additional expansive corrosion products leading to staining, cracking and spalling of the concrete.

Nitrite ions contained in RHEOCRETE CNI admixture are effective in preventing ferrous chloride complex formation by reacting with defective ferrous oxide ions prior to chloride attack and reforming the passive layer. Nitrite ions surround the defective ferrous oxide ion and convert it to a more stable ferric ion species less susceptible to corrosion. This oxidation reaction serves to repassivate the reinforcing steel and re-establish the barrier between the steel and chlorides that initiate corrosion.

Applications

RHEOCRETE CNI admixture will effectively inhibit corrosion in all types of steel reinforced concrete including pre-cast/pre-stressed and post-tensioned applications.

RHEOCRETE CNI admixture is recommended for use in parking garages, bridge decks, marine structures, slabs, floors and other reinforced concrete applications requiring corrosion protection against chlorides from deicing salts or marine exposure. RHEOCRETE CNI admixture will also inhibit the potentially corrosive effects of chloride-bearing concrete-making ingredients.

Compatibility

RHEOCRETE CNI admixture may be used with Portland cements and mineral admixtures approved under ASTM, AASHTO, or CRD specifications. It is compatible with other chemical admixtures, including water reducers, superplasticisers, retarders and air entrainers. Chemical admixtures should be added separately to the concrete to ensure desired results.

Concrete Setting Time

Concrete setting times may be accelerated with the use of RHEOCRETE CNI admixture. If desired, a retarding or hydration control admixture may be added to the concrete mixture to offset the acceleration effects of RHEOCRETE CNI admixture.

Adding Value to Concrete



The Chemical Company

RHEOCRETE[®] CNI

Please contact your local BASF representative for additional information on set-balancing admixtures for concrete.

Dosage

RHEOCRETE CNI is recommended for use at a rate of 5.0 to 30.0ltr/m³ of concrete, depending upon the severity of the corrosion environment and the anticipated chloride loading of the structure.

RHEOCRETE CNI may be used to offset the potentially corrosive effects of chloride-bearing concrete-making ingredients, and in applications where the initial chloride ion content of the concrete may exceed code requirements or other specified chloride limits.

Chloride protection limits for RHEOCRETE CNI are as given in the dosage table.

The limits for applications involving the use of chloride-bearing materials are based on a critical chloride-to-nitrite ratio of 0.90 in accordance with the recommendations of the Federal Highway Administration (FHWA). These limits may also be used in very severe corrosion environments for enhanced protection, if desired.

The chloride protection limits given for all other applications, such as parking structures and bridges, are based on critical chloride-to-nitrite ratios that range from 1.20 to 1.50. Please contact your local BASF representative for additional information regarding dosage rates of RHEOCRETE CNI for your application.

RHEOCRETE CNI Dosage ltr/m ³	Chloride Protection Limit, kg/m ³	
	With Chloride-Bearing Materials	All Other Applications
5.0	1.2	---
10.0	2.4	3.6
15.0	3.6	5.9
20.0	4.8	7.7
25.0	6.0	8.9
30.0	7.2	9.5

BASF recommends that steel reinforced concrete structures that will be exposed to chlorides in service should be designed in accordance with ACI 318, ACI 357, CSA, AASHTO or other applicable codes.

Chemical Composition

RHEOCRETE CNI admixture contains a minimum of 30% calcium nitrite by mass as an active ingredient. RHEOCRETE CNI is identical in composition and mechanism to other commercially available 30% calcium nitrite corrosion-inhibiting admixtures, and at equal dosage rates, provides similar performance and corrosion protection.

The water content of RHEOCRETE CNI admixture is approximately 7.3 pounds per gallon. This water contributes to the consistency of the concrete mixture and the hydration of the cementitious materials. The water contributed by RHEOCRETE CNI should be used in the calculation of the water to cementitious material ratio of the concrete.

Non-chloride

RHEOCRETE CNI admixture will not initiate or promote corrosion of reinforcing steel embedded in concrete, pre-stressed concrete or concrete placed on galvanised steel floor and roof systems. Neither calcium chloride nor any chloride-based ingredients are used in the manufacture of RHEOCRETE CNI.



Temperature Precaution

RHEOCRETE CNI admixture can be stored at temperatures between -12° to 38°C. If RHEOCRETE CNI admixture freezes, it can be fully reconstituted by thawing and mechanical agitation.

Do not use pressurised air for agitation.

RHEOCRETE[®] CNI

FOURIER TRANSFORM INFRARED (FT-IR) SPECTRAL COMPARISON

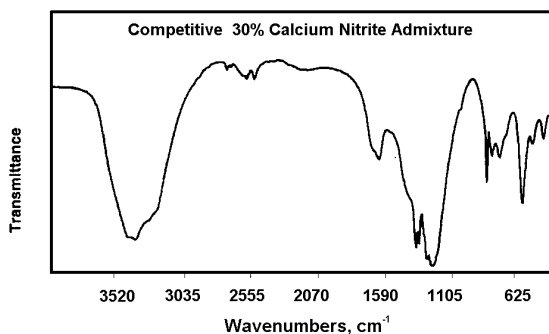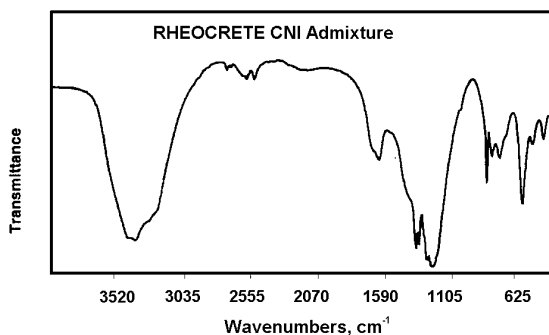

Storage

Store under cover, out of direct sunlight and protect from extremes of temperature. Powder should be protected from rain and stored off the ground on pallets.

Failure to comply with the recommended storage conditions may result in premature deterioration of the product or packaging. For specific storage advice, consult BASF's Technical Services Department.

Shelf Life

Up to 24 months if stored according to manufacturer's instructions in unopened containers.

Note

Field service, where provided, does not constitute supervisory responsibility. For additional information, contact your local BASF representative.

BASF reserves the right to have the true cause of any difficulty determined by accepted test method.

Quality Statement

All products manufactured by BASF Egypt, or imported from BASF affiliate companies world-wide, are manufactured to procedures certified to conform to the quality, environment, health & safety management systems described in the ISO 9001:2000, ISO 14001:2004 & OHSAS 18001:1999 standards.

12/07 BASF-EG

* Properties listed are only for guidance and are not a guarantee of performance.

BASF-CC, Egypt
55, St. 18, Maadi Sarayat
11431 Cairo, Egypt
Factory: Sadat City, Piece 118
Zone 4

Tel.: +2 012 393 98 44
Tel.: +2 012 398 67 78
Tel.: +2 012 390 22 35
Tel.: +2048 2604842
Fax: +2048 2604757

Whilst any information contained herein is true, accurate and represents our best knowledge and experience, no warranty is given or implied with any recommendations made by us, our representatives or distributors, as the conditions of use and the competence of any labour involved in the application are beyond our control.

e-mail: enquire.egypt@basf.com, website: www.basf-cc.com.eg

As all BASF technical datasheets are updated on a regular basis, it is the user's responsibility to obtain the most recent issue. Most recent issue is available on the website at www.basf-cc.com.eg

